


Technical Data Sheet

Polyester Curing

Ketone peroxides (Ambient temperature)

CUROX[®] M-202

Methyl ethyl ketone peroxide
CAS#1338-23-4
Liquid mixture

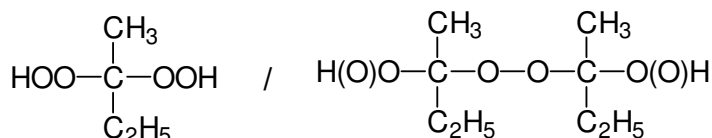

Description:

Colourless, mobile liquid, consisting of peroxides based on methyl ethyl ketone, essentially desensitised with aliphatic ester. This ketone peroxide is used as an initiator (radical source) in the curing of unsaturated polyester resins. Main application: curing of moulded parts at ambient temperature in combination with cobalt accelerators.

Technical Data:

Appearance colourless liquid
Active oxygen approx. 9.0 – 9.3% w/w
De-sensitising agent aliphatic ester
Density at 20°C approx. 1.01 g/cm³
Viscosity at 20°C approx. 16 mPa·s
Miscibility e.g. unsaturated polyester resins, alcohols, esters
Critical temperature (SADT) approx. 60°C
Cold storage stability to below -25°C
Recommended storage temperature below 30°C
Maintenance of activity at 25°C min. 6 months

Application:

POLYESTER CURING: Standard curing agent for all UP resin types at ambient temperature in combination with cobalt accelerators. Especially suitable for resins based on ortho- and isophthalic acid respectively. Standard dosage level: 1-3% as supplied, with 0.2-2% of a 1% cobalt solution.

"Shelf life" (gel time of resin + peroxide) usually only a few hours, depending on temperature and resin type. "Pot life" (gel time of resin + peroxide + accelerator) relatively short, but may be prolonged by adding Inhibitor TC-510. Thus, the mould release factor ($f_{MR} = t_{MR}/t_{gel}$) can be improved considerably.


CURING PERFORMANCE: Moderate evolution of heat. Relatively long mould release time, moderate mould release factors. Temperatures below 20°C prolong curing times considerably, alternatively cobalt / amine accelerators should then be used.

PROCESSING METHODS: Particularly hand lay-up, spray lay-up, centrifugal casting, filament winding, casting of resins, and surface coatings (putties, fillers, gelcoats and topcoats).

SPRAY EQUIPMENT: Use spray equipment in accordance with manufacturer's instructions. Ensure all safety devices are operational. Do not clear gun by spraying MEKP into the air.

Activity:**Curing of orthophthalicacid resin**

Curing: DIN 16945 (20 g in glas tubes, 25 °C)						
Formulation (parts by weight)						
Medium reactive o-phthalic acid resin type	100	100	100	100	100	100
CUROX [®] M-202	2	2	2	2	1	1
Accelerator C-101 (Cobaltoctoate)	2	1	0,5	0,2	1	0,5
Cure times (minutes)						
Gel time (t_{gel})	2,0	3,0	6,5	23,5	8,0	16,5
Time to peak (t_{max})	14,5	17,0	22,0	51,5	35,5	56,5
Peak temperature (°C)	141	141	137	108	107	89

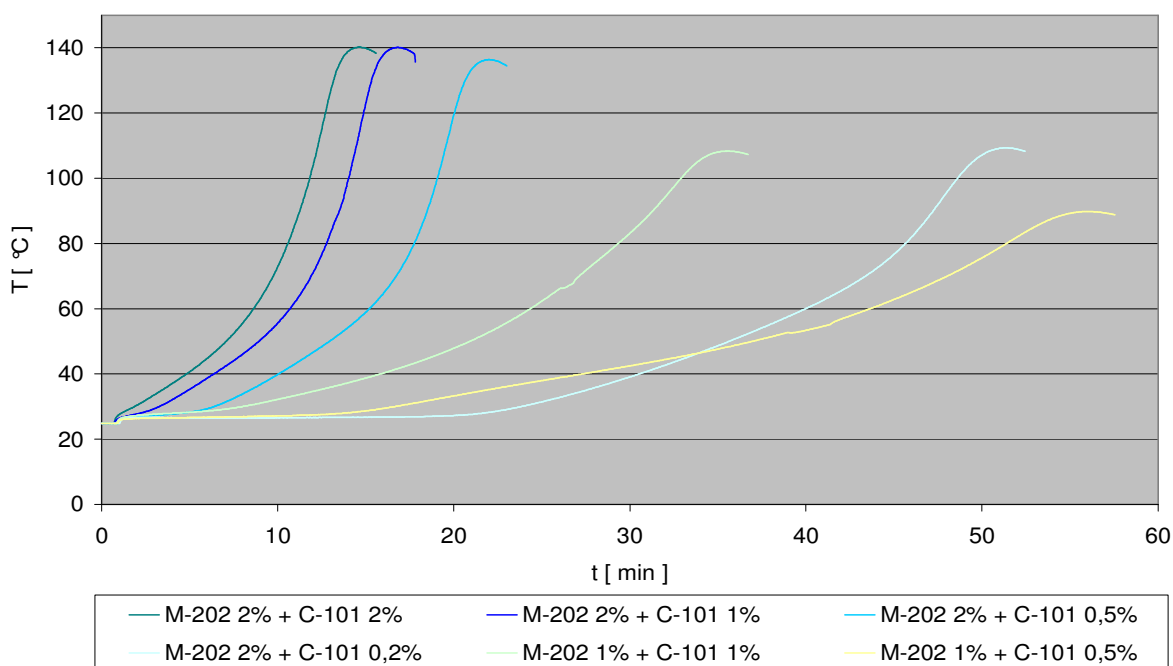**Contact:**

<http://www.united-initiators.com>

Disclaimer

This information and all further technical advice are reflecting our present knowledge and experience based on internal tests with local raw materials with the purpose to inform about our products and applications. The information should not be construed as guaranteeing specific properties of products described or their suitability for a particular application, nor as providing complete instructions for use. The information implies no guarantee for product and shelf life properties, nor any liability or other legal responsibility on our part, including with regard to existing third party intellectual property rights, especially patent rights. We reserve the right to make any changes according to technological progress or further developments.

Application and usage of our products based on our technical advice is out of our control and sole responsibility of the user. The user is not released from the obligation to conduct careful inspection and testing of incoming goods in order to verify the suitability for the intended application.

